

This is the author's version of a work that was accepted for publication *Geochimica et Cosmochimica Acta*. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in *Geochimica et Cosmochimica Acta*, Volume 127, 15 February 2014, Pages 107–119 <http://doi.org/10.1016/j.gca.2013.10.043>.

## Synthesis, Characterization and Thermochemistry of Synthetic Pb-As, Pb-Cu and Pb-Zn Jarosites

Ferenc Lázár Forray<sup>1,2</sup>, A.M.L. Smith<sup>3,5,6</sup>, A. Navrotsky<sup>2,\*</sup>, K. Wright<sup>4</sup>, K.A. Hudson-Edwards<sup>5</sup>, W.E. Dubbin<sup>6</sup>

<sup>1</sup> Department of Geology, Babeş-Bolyai University, M.Kogălniceanu 1, 400084 Cluj-Napoca, Romania

<sup>2</sup> Peter A Rock Thermochemistry Laboratory and NEAT ORU, University of California Davis, 1 Shields Avenue, Davis, CA 95616, USA.

<sup>3</sup> Davy Faraday Research Laboratory, The Royal Institution of Great Britain, 21 Albemarle Street, London, W1S 4BS, UK.

<sup>4</sup> Nanochemistry Research Institute, Department of Applied Chemistry, Curtin University of Technology, GPO Box U1987, Perth, WA 6845.

<sup>5</sup> Department of Earth and Planetary Sciences, Birkbeck, University of London, Malet Street, London, WC1E 7HX, UK.

<sup>6</sup> Department of Earth Science, The Natural History Museum, Cromwell Road, London, SW7 5BD, UK.

### Abstract

The enthalpy of formation from the elements of well characterized Pb-As, Pb-Cu, and Pb-Zn synthetic jarosites, corresponding to chemical formulas  $(\text{H}_3\text{O})_{0.68\pm 0.03}\text{Pb}_{0.32\pm 0.002}\text{Fe}_{2.86\pm 0.14}(\text{SO}_4)_{1.69\pm 0.08}(\text{AsO}_4)_{0.31\pm 0.02}(\text{OH})_{5.59\pm 0.28}(\text{H}_2\text{O})_{0.41\pm 0.02}$ ,  $(\text{H}_3\text{O})_{0.67\pm 0.03}\text{Pb}_{0.33\pm 0.02}\text{Fe}_{2.71\pm 0.14}\text{Cu}_{0.25\pm 0.01}(\text{SO}_4)_{2\pm 0.00}(\text{OH})_{5.96\pm 0.30}(\text{H}_2\text{O})_{0.04\pm 0.002}$  and  $(\text{H}_3\text{O})_{0.57\pm 0.03}\text{Pb}_{0.43\pm 0.02}\text{Fe}_{2.70\pm 0.14}\text{Zn}_{0.21\pm 0.01}(\text{SO}_4)_{2\pm 0.00}(\text{OH})_{5.95\pm 0.30}(\text{H}_2\text{O})_{0.05\pm 0.002}$ , was measured by high temperature oxide melt solution calorimetry and gave  $\Delta H_f^\circ = -3691.2 \pm 8.6$  kJ/mol,  $\Delta H_f^\circ = -3653.6 \pm 8.2$  kJ/mol, and  $\Delta H_f^\circ = -3669.4 \pm 8.4$  kJ/mol, respectively. Using estimated entropies, the standard Gibbs free energy of formation from elements at 298 K  $\Delta G_f^\circ$  of the three compounds were calculated to be  $-3164.8 \pm 9.1$  kJ/mol,  $-3131.4 \pm 8.7$  kJ/mol, and  $-3153.6 \pm 8.9$  kJ/mol, respectively. Based on these free energies, their  $\log K_{sp}$  values are  $-13.94 \pm 1.89$ ,  $-4.38 \pm 1.81$  and  $-3.75 \pm 1.80$ , respectively. For this compounds, a  $\log_{10}\{\text{Pb}^{2+}\}$  - pH diagram is presented. The diagram shows that the formation of Pb-As jarosite may decrease aqueous arsenic and lead concentrations to meet drinking water standards. The new thermodynamic data confirm that transformation of Pb-As jarosite to plumbojarosite is thermodynamically possible.

### 1. Introduction

Jarosite is a member of the isostructural jarosite - alunite group of minerals that has a general formula  $\text{AB}_3(\text{TO}_4)_2(\text{OH})_6$ , where A represents cations with a coordination number  $\geq 9$ , and B and T represent cations with octahedral (O) and tetrahedral (T) coordination, respectively (Hawthorne et al., 2000; Jambor, 1999). In ideal jarosite  $[\text{KFe}_3(\text{SO}_4)_2(\text{OH})_6]$ , the B site cation is Fe(III), the A site is occupied by a cation (mainly  $\text{K}^+$ , but also  $\text{H}_3\text{O}^+$ , hydronium; Brophy and Sheridan, 1965; Dutrizac and Kaiman, 1976; Kubisz, 1970; Ripmeester et al., 1986) in 12-fold coordination, and the T site is filled by sulphate ( $\text{SO}_4^{2-}$ ) (Brophy and Sheridan, 1965; Kubisz, 1964). Jarosite minerals are important in acid Earth surface environments and metallurgy (Bigham and Nordstrom, 2000; Dutrizac and Jambor, 2000), because the A, B and T sites can be filled with metal and metalloid ions (e.g.,  $\text{Pb}^{2+}$  in the A site,  $\text{Cu}^{2+}$  and  $\text{Zn}^{2+}$  in the B site,  $\text{As}^{5+}$  in the T site; Dutrizac and Jambor, 2000). Zinc atoms have also been found to occupy trigonal bipyramidal sites in half of the available six-membered rings of the layers of octahedral in a monoclinic segnitite ( $\text{PbFe}_3\text{H}(\text{AsO}_4)_2(\text{OH})_6$ )-related mineral by Grey et al. (2008), giving  $\text{PbZn}_{0.5}\text{Fe}_3(\text{AsO}_4)_2(\text{OH})_6$ . The Cu and Zn containing plumbojarosite (beaverite) is an important phase present in the hydrometallurgy of sulphide concentrates (Jambor and Dutrizac, 1985), and beudantite  $\text{PbFe}_3(\text{AsO}_4)(\text{SO}_4)(\text{OH})_6$  has been described from As and Pb

contaminated agricultural soil (Chiang et al., 2010), mine waste and tailings (Dill et al., 2010; Romero et al., 2010; Roussel et al., 2000), from hydrometallurgical processes (Roca et al., 1999) and from bauxite waste red mud (McConchie et al., 2006). Jarosite has also been detected on Mars, and shown to be stable under likely Martian temperature conditions (Navrotsky et al., 2005), giving evidence this planet's surface once contained water (Klingelhöfer et al., 2004). Kocourková et al. (2011) suggested that beudantite is better suited for long-term arsenic storage than jarosite, which appears to be less stable. To understand mineral stability in different environments, thermodynamic data are required. This study reports new thermochemical data for these minerals: enthalpies of formation obtained by solution calorimetric measurements, estimated entropies, and calculated Gibbs free energies of formation. We have used synthetic analogues for our work because we are able to constrain their compositions and conditions of formation.

## 2. Methods and Materials

### 2.1. Synthesis

Pb-As jarosite was made following the method of Alcobe et al. (2001) from a 1 L solution containing 0.054 M  $\text{Fe}_2(\text{SO}_4)_3 \cdot 5\text{H}_2\text{O}$  and 0.00946 M  $\text{H}_3\text{AsO}_4$ . The synthesis of Pb-Cu jarosite is described in Hudson-Edwards et al. (2008). The syntheses of the Pb-Cu and Pb-Zn jarosite compounds were based on the methods of Dutrizac and Dinardo (1983) and Jambor and Dutrizac (1983, 1985). The Pb-Cu- and Pb-Zn-jarosite compounds were made from a one litre solution containing 0.054 M  $\text{Fe}_2(\text{SO}_4)_3 \cdot 5\text{H}_2\text{O}$  and 0.02 M  $\text{H}_2\text{SO}_4$ , with the addition of either 0.315M  $\text{CuSO}_4 \cdot 5\text{H}_2\text{O}$  (for Pb-Cu-jarosite) or 0.306 M  $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$  (for Pb-Zn jarosite). In all three cases, the solutions were placed in 2 L reaction vessels fitted with spiral condensers, then heated by means of a sand bath to 95 °C (1 atm) with constant stirring (400 rpm). When the solution temperatures reached 95 °C, 200 mL of 0.03 M  $\text{Pb}(\text{NO}_3)_2$  (Aldrich) was added, with stirring, to each solution at a rate of 6 mL  $\text{hr}^{-1}$ . Once all the  $\text{Pb}(\text{NO}_3)_2$  had been added, the precipitates were stirred for a further 5 h, after which they were allowed to settle and the residual solutions decanted. The precipitates were then washed several times with ultrapure water (18 M $\Omega$   $\text{cm}^{-1}$ ) and dried at 110 °C for 24 h.

### 2.2. Characterization

The precipitation products were identified using powder X-ray diffraction (XRD) analysis at 25 °C with a Philips PW1050 vertical powder diffractometer operated at 35 kV and 30 mA. The diffractometer used  $\text{Co K}\alpha_{1,2}$  radiation ( $\lambda_{\alpha_1} = 1.788965 \text{ \AA}$  and  $\lambda_{\alpha_2} = 1.792850 \text{ \AA}$ ); and the X-ray tube was a long fine-focus type (0.8 × 12 mm). The 2 $\theta$  angle range was 5 to 155 °. The step size was 0.025 ° 2 $\theta$  and the measuring time was 10 seconds per step. Unit cell parameters were calculated through Rietveld refinement using GSAS (Larson and Von Dreele, 2000; Toby, 2001) and the 'model free' Le Bail method (Le Bail et al., 1988), where individual ' $|F_{\text{obs}}|$ ' are obtained by Rietveld decomposition from arbitrarily identical values. In addition to the structure factors, free refinement was made of the lattice parameters constrained according to the rhombohedral symmetry of the space group in the centred hexagonal setting, background, profile parameters, and the instrumental zero-point. In all cases, a pseudo-Voigt profile was used. The errors calculated using this method are small, but we acknowledge that they may be slightly larger than reported, due to the program not incorporating all sources of error (cf. Herbstein, 2000; Schwarzenbach et al., 1989).

For quantitative total elemental analysis, approximately 60 mg of each of the synthetic jarosite compounds were dissolved in polypropylene beakers by adding HCl dropwise, with stirring, until no solid remained. The acidified solutions were then diluted to 50 mL with 2 %  $\text{HNO}_3$ , and analysed for Pb, Fe, Cu, Zn, S, As, as appropriate for each compound, by inductively coupled plasma optical emission spectrometry (ICP-OES) using a simultaneous solid-state detector (CCD) (Varian Vista-Pro, axial configuration). All analytical ICP-OES results were within one standard deviation of the mean. Fourier transform infrared (FTIR) spectroscopy was used to characterize the vibrational modes within the synthetic jarosite compounds. Spectra were collected with a Perkin-Elmer Spectrum One FTIR spectrometer using the KBr pellet ( $\varnothing 13 \text{ mm}$ ) technique. The spectra (400 – 4000  $\text{cm}^{-1}$ ) were recorded in transmission mode immediately after pellet preparation. Five scans were accumulated, each with a resolution of 4  $\text{cm}^{-1}$ .

A Philips XL30 FEG scanning electron microscope was used to determine the particle morphology of the synthetic jarosite compounds. The samples were mounted on 5 mm diameter aluminium stubs by araldite adhesive, once dry the samples were coated in 95 % Au and 5 % Pd. The operating conditions for

the SEM were 7.0 kV accelerating voltage, at a spot size of 2.0 nm, 6500× magnification and an SE detector was used.

A Micromeritics Gemini III 2375 surface area analyser was used to determine the surface area of the synthetic jarosite compounds. Each sample was de-gassed in N<sub>2</sub> for 24 hrs at 100 °C prior to analysis. The surface areas were calculated through a multi-point (5 points) Brunauer-Emmett-Teller (BET) (Brunauer et al., 1938) surface area measurement using N<sub>2</sub> gas at 77 K as the adsorbate.

### 2.3. Calorimetry

High-temperature oxide melt drop solution calorimetry was run at 700 °C using a Tian-Calvet twin calorimeter and sodium molybdate (3Na<sub>2</sub>O·4MoO<sub>3</sub>) solvent. A detailed description of the calorimetric technique can be found elsewhere (Navrotsky, 1977, 1997). Sample pellets of ~5 mg were dropped into a platinum crucible containing the solvent, located in the hot zone of the calorimeter. During the experiments, oxygen was flushed through the gas space above the melt (~35 ml/min) and bubbled through the solvent (~5 to 7 ml/min) to maintain oxidizing conditions, stir the melt, and remove the evolved water. The end of the reaction in the solvent was judged by the return of the calorimetric signal to its initial (baseline) value. The measured heat effect, called the enthalpy of drop solution ( $\Delta H_{ds}$ ), is the sum of the heat content of the sample, its heat of solution, and any heat related to gas release, oxidation, or reduction. The enthalpy of formation ( $\Delta H_f^0$ ) of a given compound can be determined from  $\Delta H_{ds}$  through the use of an appropriate thermodynamic cycle (see Table 1, 2, 3, and 4).

The final state in these calorimetric experiments is a dilute solution in 3Na<sub>2</sub>O·4MoO<sub>3</sub> of dissolved Pb, Zn, As and Fe oxides and sulphate species and gaseous H<sub>2</sub>O, all at 700°C. Previous studies on simple sulphates and jarosite phases (Drouet and Navrotsky, 2003; Forray et al., 2005; Majzlan et al., 2002) have shown that all the sulphur is retained in the melt as SO<sub>4</sub><sup>2-</sup>, rather than emitted into the gas phase.

Prior to this work, the oxidation state of arsenic dissolved in the sodium molybdate solvent, at 700 °C was not known. To verify the arsenic state in the solvent, we used a thermodynamic cycle involving high purity Alfa Aesar As<sub>2</sub>O<sub>3</sub> (99.996 %) and As<sub>2</sub>O<sub>5</sub> (99.9%) (see below).

## 3. Results and Discussion

The results of all of the characterisation techniques are outlined and discussed below. Some data for the synthetic Pb-Cu jarosite have already been presented in Hudson-Edwards et al. (2008), but for completeness, are summarized below.


### 3.1. Solid characterisation

#### 3.1.1. X-ray diffraction and formula determination

The jarosite synthesis produced yellow precipitates with Munsell colours 10YR 8/8 (Pb-As jarosite), 10YR 7/5 (Pb-Cu jarosite) and 10YR 7/6 (Pb-Zn jarosite). Comparison of the powder X-ray diffraction patterns with those in the International Centre for Diffraction Data Powder Diffraction Files proved problematic, as no ICDD PDF files for synthetic beudantite and beaverite-Cu or -Zn exist. For this reason, ICDD PDF files for natural beudantite (19-0689) and beaverite (17-0476) were used to identify the structures of the synthetic Pb-As, Pb-Cu and Pb-Zn jarosites. All the diffraction peaks identified from the XRD pattern match the PDF files. No other mineral phases were present in the synthesized compounds at detectable levels by X-ray diffraction (Fig. 1a-c).

The calculated lattice parameters of the synthetic Pb-As jarosite are  $a_0 = 7.3417(8)$  Å and  $c_0 = 16.9213(6)$  Å, similar to the standard ICDD PDF file values ( $a_0 = 7.32$  Å;  $c_0 = 17.02$  Å). The calculated lattice parameters of the synthetic Pb-Cu and Pb-Zn jarosites are  $a_0 = 7.3208(8)$  Å and  $c_0 = 17.0336(7)$  Å and  $a_0 = 7.3373(7)$  Å and  $c_0 = 16.9268(7)$  Å, respectively; the standard ICDD PDF file values were  $a_0 = 7.20$  Å and  $c_0 = 16.94$  Å. Giuseppetti and Tadini (1980) carried out a structural study of osarizawaite, the isostructural alunite equivalent of beaverite. They found that Al(III), Fe(III) and Cu(II) had random occupancy in the B-sites and that a replacement of Fe(III) ( $r = 0.67$  Å) and Al(III) ( $r = 0.50$  Å) by Cu(II) ( $r = 0.83$  Å) should expand the T-O-T jarosite structure mainly along  $a_0$ . The length of  $c_0$  was predicted to remain relatively constant, however, because expansion along  $a_0$  permits greater interpenetration of neighbouring sheets, thus reducing the amount of increase otherwise expected. Jambor and Dutrizac (1983) investigated a synthetic

Pb-Zn-jarosite with Zn(II) ( $r = 0.74 \text{ \AA}$ ) as the only divalent ion in the B-site and found that the c-axis was similar or slightly smaller, and the a-axis larger, than that of the beaverite with Cu(II) in the B-site.

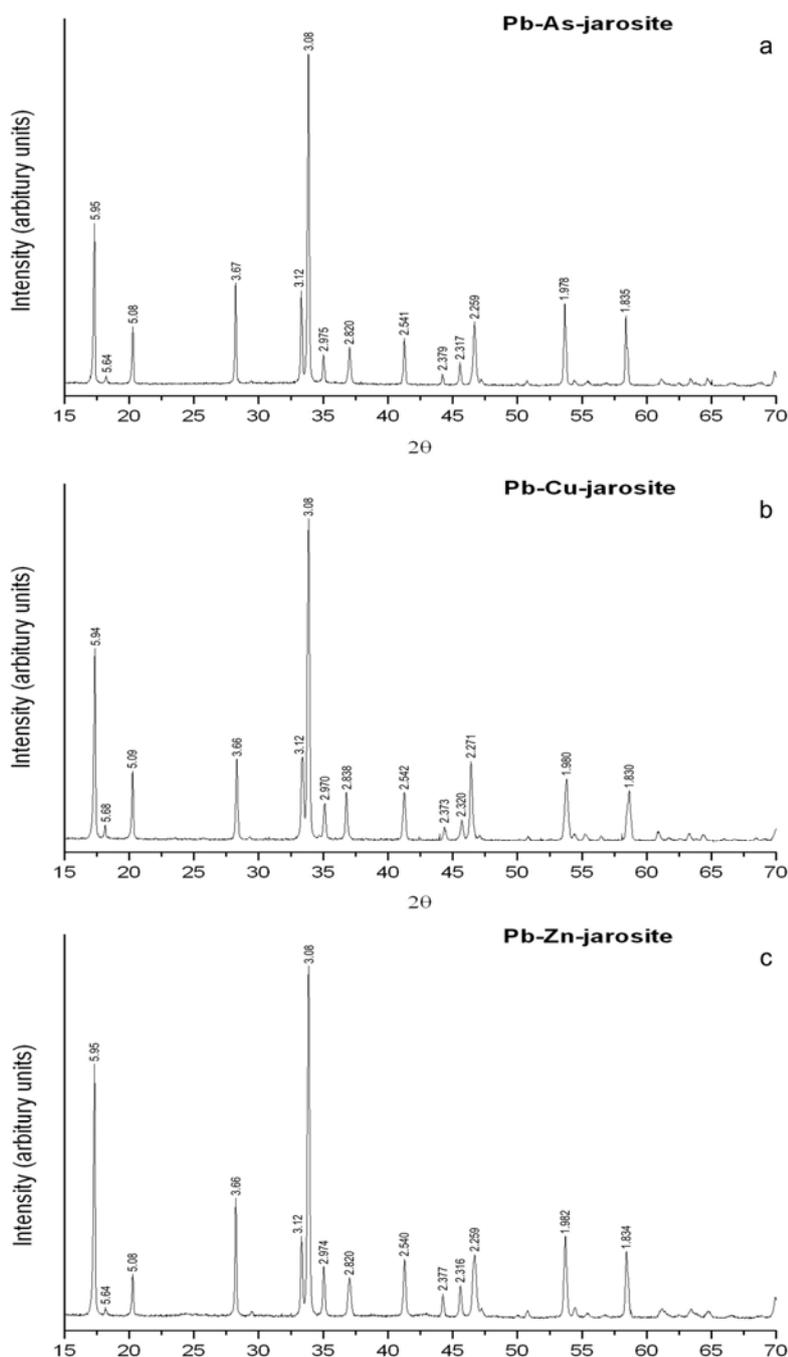

**Fig 1.** Power X-ray diffraction patterns for synthetic compounds (a) Pb-As-jarosite (b) Pb-Cu-jarosite, (c) Pb-Zn-jarosite. 2-theta range 15-70°.

Therefore, although Cu and Zn are divalent ions of similar size, their effects on the cell parameters are distinctly different. Jambor and Dutrizac (1983) concluded that the length of  $a_0$  seemed to be governed principally by the proportions of Fe(III), Cu(II), Zn(II), and the total number of ions in the B-site. When comparing the synthetic Pb-Cu and Pb-Zn jarosites to the ICDD PDF standard, we see some small difference in  $a_0$  values. The main reason for this is the different amounts of Fe(III), Cu(II), Zn(II) in the B-site; the natural ICDD PDF samples will probably have fewer vacancies and therefore higher site occupancy in comparison to the synthetic analogues.

The  $\text{As}_2\text{O}_3$  and  $\text{As}_2\text{O}_5$  compounds used to test the arsenic state in the solvent at 700 °C were analyzed by X-ray powder diffraction. The diffraction pattern indicated a single  $\text{As}_2\text{O}_3$  phase similar to arsenolite (JCPDF 36-1490). For  $\text{As}_2\text{O}_5$ , the pattern showed the presence of a major phase (JCPDF 71-0419) and a minor one (JCPDF 01-0260). For the  $\text{As}_2\text{O}_5$  compound a subsequent heat treatment procedure (annealing in sealed quartz tube) was used to eliminate the minor phase. Both samples were handled in a glove box under controlled environment due to the arsenic toxicity and to  $\text{As}_2\text{O}_5$  hygroscopicity. The Rietveld refinements of the X-ray diffraction pattern give the unit cell parameters for the arsenolite as  $a_0 = 11.09538 \pm 0.00077 \text{ \AA}$ , and for  $\text{As}_2\text{O}_5$   $a_0 = 8.64092 \pm 0.00012 \text{ \AA}$ ,  $b_0 = 8.44074 \pm 0.00009 \text{ \AA}$ , and  $c_0 = 4.62406 \pm 0.00007 \text{ \AA}$ .

Atomic percentages of the A-, B- and T-site (for the Pb-As jarosite) elements were determined using the total elemental analysis data. The formulas of the synthetic Pb-As, Pb-Cu and Pb-Zn jarosites were calculated using the modified formula of Kubisz (1970). Using this formula, the  $\text{SO}_4$  is set at 2 and the other elements are calculated using the elemental data.


Errors were estimated using the analytical error for the total elemental analysis of 5%. The calculated formulas are  $(\text{H}_3\text{O})_{0.68 \pm 0.03} \text{Pb}_{0.32 \pm 0.002} \text{Fe}_{2.86 \pm 0.14} (\text{SO}_4)_{1.69 \pm 0.08} (\text{AsO}_4)_{0.31 \pm 0.02} (\text{OH})_{5.59 \pm 0.28} (\text{H}_2\text{O})_{0.41 \pm 0.02}$ ,  $(\text{H}_3\text{O})_{0.67 \pm 0.03} \text{Pb}_{0.33 \pm 0.02} \text{Fe}_{2.71 \pm 0.14} \text{Cu}_{0.25 \pm 0.01} (\text{SO}_4)_{2 \pm 0.00} (\text{OH})_{5.96 \pm 0.30} (\text{H}_2\text{O})_{0.04 \pm 0.002}$  and  $(\text{H}_3\text{O})_{0.57 \pm 0.03} \text{Pb}_{0.43 \pm 0.02} \text{Fe}_{2.70 \pm 0.14}$

$\text{Zn}_{0.21\pm 0.01}(\text{SO}_4)_{2\pm 0.00}(\text{OH})_{5.95\pm 0.30}(\text{H}_2\text{O})_{0.05\pm 0.002}$ , respectively. In these formulas, we adopt the conventional formula for members of the jarosite family by showing that Zn substitutes for Fe rather than occupying the trigonal bipyramidal identified by Grey et al. (2008). These formulas suggest that the synthetic jarosite compounds produced are not end-members of beaverite or beudantite, but their crystal structures (based on their XRD patterns) match those of these minerals. For this reason, we will continue to call the synthetic phases 'Pb-As jarosite', 'Pb-Cu jarosite', and 'Pb-Zn jarosite'.

### 3.1.2. Fourier transform infrared spectroscopy (FTIR)

Comparison of the FTIR spectra for the synthetic compounds prepared in this study (Fig. 2a-c) with those previously reported confirm that the phases synthesised are jarosite analogues and that no other phases have been detected (Baron and Palmer, 1996; Drouet and Navrotsky, 2003; Powers et al., 1975; Serna et al., 1986).




The O-H stretching ( $\nu_{\text{OH}}$ ) band in the region 2900 to 3700  $\text{cm}^{-1}$  shifts toward lower frequencies for the synthetic Pb-As (3343  $\text{cm}^{-1}$ ), Pb-Cu (3362  $\text{cm}^{-1}$ ) and Pb-Zn jarosites (3357  $\text{cm}^{-1}$ ), compared with end-member synthetic K-jarosite (3385  $\text{cm}^{-1}$ ) (Smith et al., 2006). The synthetic Pb-As jarosite has a relatively low  $\nu_{\text{OH}}$  vibration frequency (i.e., 1634  $\text{cm}^{-1}$ ) due to the partial substitution of arsenate for sulphate; arsenate is represented in the spectra as two peaks at 813 and 855  $\text{cm}^{-1}$  (these correspond to the  $\nu_1(\text{AsO}_4^{3-})$  and  $\nu_3(\text{AsO}_4^{3-})$  modes, respectively, Fig. 2a).

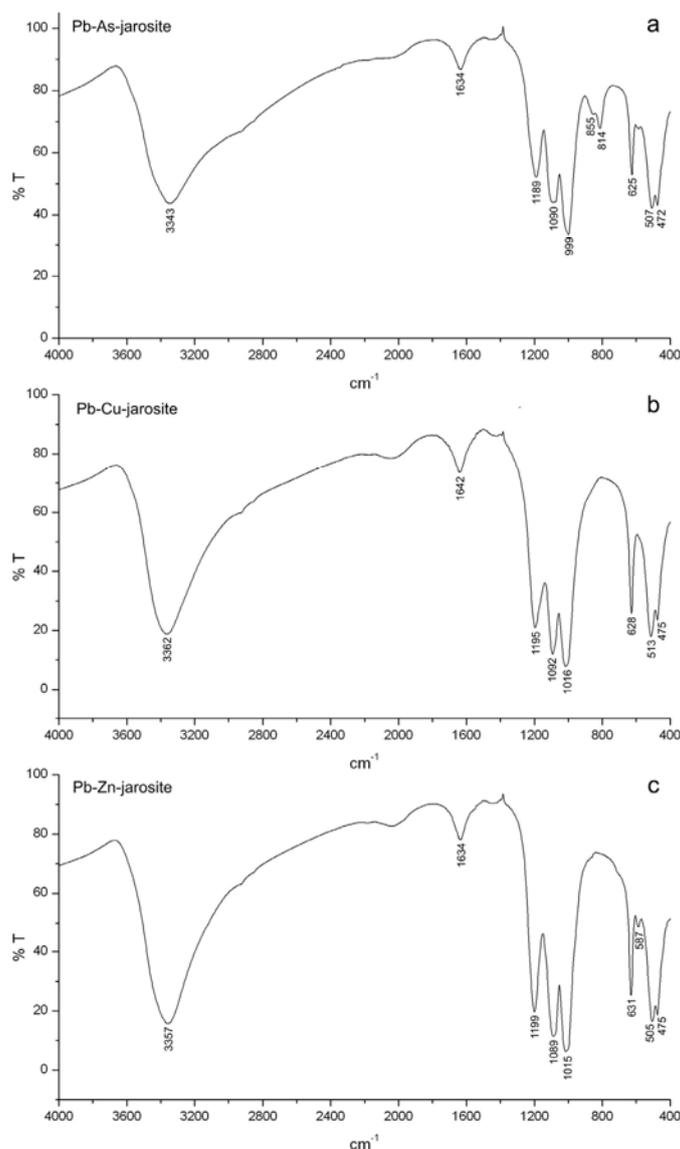

**Fig 2.** Fourier transform infrared spectra (FTIR) of synthetic compounds (a) Pb-As-jarosite, (b) Pb-Cu-jarosite, (c) Pb-Zn-jarosite. The range was 400 – 4000  $\text{cm}^{-1}$  wavenumbers with a resolution of 4  $\text{cm}^{-1}$ , five scans were accumulated. The main vibrational bands in the spectra are marked.

### 3.1.3. Morphology and surface area

The synthetic Pb-As jarosite crystals are intergrown (2-3  $\mu\text{m}$  across), with a pseudo-rhombohedral to globular morphology (Fig. 3a). The crystal morphologies of the synthetic Pb-Cu and Pb-Zn jarosites (Fig. 3b,c) are very similar, in that the precipitates occur as spherical or cauliflower-like aggregates of individual crystals with diameters < 2  $\mu\text{m}$  across. The sizes of individual crystals are so small that individual faces are distinguishable in some cases only. At higher magnification, it is possible to see that the synthetic crystals

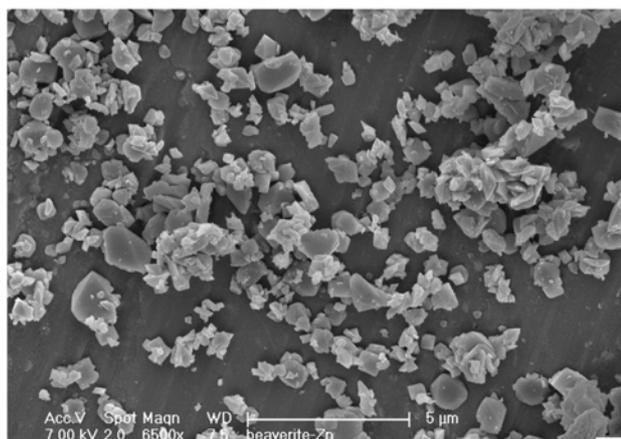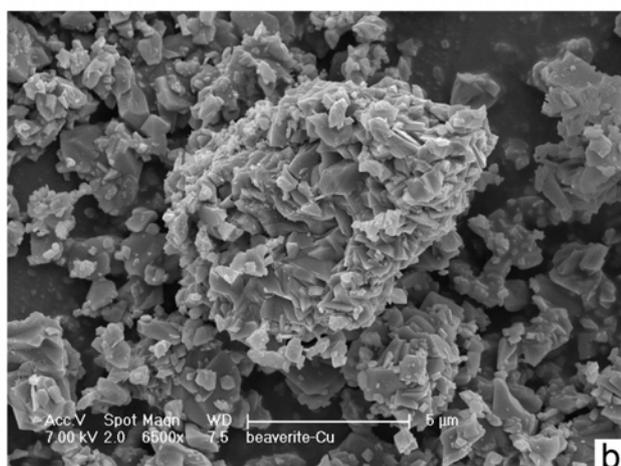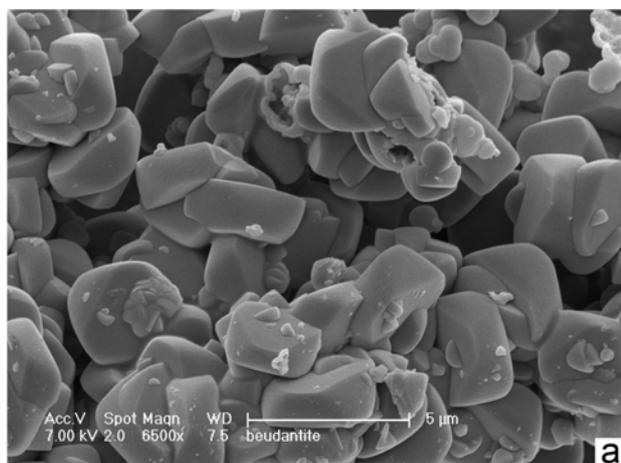

**Fig. 3.** Scanning electron micrograph (SEM) images of: synthetic compounds (a) Pb-As-jarosite, (b) Pb-Cu-jarosite, (c) Pb-Zn-jarosite. Operating conditions were 7.0 kV, spot-size 2.0, magnification 6500x. The scale bar on the micrographs is 5  $\mu\text{m}$ .

have a euhedral habit. The surface areas for the synthetic Pb-As, Pb-Cu- and Pb-Zn jarosites are  $9.58 \pm 0.09(6) \text{ m}^2\text{g}^{-1}$ ,  $3.19 \pm 0.03(4)$  and  $3.67 \pm 0.02(5)$ , respectively. The small surface areas and sharp X-ray diffraction peaks show that these are not nanosized crystals.

### 3.2. Calorimetric data

To verify that arsenic oxide sample dropped into the solvent in the hot zone of the calorimeter is not expelled as a gas, a “furnace test” was performed in similar conditions than those in the calorimeter. The furnace setup had two gas inlets, and one outlet (the dropping tube). The gas outlet was connected to an Erlenmeyer flask (filed with ultrapure water), and the carrier gas (oxygen) was conducted through the water. We used the water from the Erlenmeyer flask also to flush the outlet tube in case some arsenic precipitated there. The water then was analyzed for arsenic content using Quick™ arsenic test kit (Industrial Test Systems, Inc.). The detection limit of the arsenic test kit is as low as 5 ppb. The “furnace test” experiment did not show any evolved arsenic.

To further test the arsenic state in the solvent, we measured the enthalpy of drop  $\Delta H_{\text{ds}}$  solution of arsenolite and  $\text{As}_2\text{O}_5$ . The enthalpy of formation ( $\Delta H_f^0$ ) of  $\text{As}_2\text{O}_3$  can be determined from  $\Delta H_{\text{ds}}$  through the use of an appropriate thermodynamic cycle. If all the arsenic remains in the solvent the reactions presented in Table 1 will give the enthalpy of formation ( $\Delta H_f^0$ ) of  $\text{As}_2\text{O}_3$ . This value can be checked with the literature values. If the determined value is not in agreement with literature data, then there is incomplete conversion of  $\text{As}^{3+}$  to  $\text{As}^{5+}$  in the solvent or a small amount of arsenic was expelled as gas that we did not detect, or some other side reaction.

To calculate the enthalpy of formation of arsenolite, beside the measured value  $\Delta H_{\text{ds}}$  for arsenolite ( $\text{As}_2\text{O}_3$ ) and  $\text{As}_2\text{O}_5$ , we need to have an accurate value for the enthalpy of formation ( $\Delta H_f^0$ ) of  $\text{As}_2\text{O}_5$ . Literature data on arsenic species have been shown to have several inconsistencies (Nordstrom and Archer, 2003). This arises from inappropriate citation, publishing slightly modified older measurements or using incorrect values by mistake and so on.

**Table 1.** Thermodynamic cycle used for the determination of  $\Delta H_f^\circ$  of  $\text{As}_2\text{O}_3$ .

| Reaction <sup>(a)</sup>                                                                                                   | $\Delta H$ (kJ/mol) <sup>(b)</sup>              |
|---------------------------------------------------------------------------------------------------------------------------|-------------------------------------------------|
| (1) $\text{As}_2\text{O}_3(\text{s}, 298) + \text{O}_2(\text{g}, 973) \rightarrow \text{As}_2\text{O}_5(\text{sol}, 973)$ | $\Delta H_{\text{ds}}(\text{As}_2\text{O}_3)$   |
| (2) $\text{As}_2\text{O}_5(\text{s}, 298) \rightarrow \text{As}_2\text{O}_5(\text{sol}, 973)$                             | $\Delta H_{\text{ds}}(\text{As}_2\text{O}_5)$   |
| (3) $2\text{As}(\text{s}, 298) + 5/2\text{O}_2(\text{g}, 298) \rightarrow \text{As}_2\text{O}_5(\text{s}, 298)$           | $\Delta H_f^\circ(\text{As}_2\text{O}_5)^{(c)}$ |
| (4) $\text{O}_2(\text{g}, 298) \rightarrow \text{O}_2(\text{g}, 973)$                                                     | $\Delta H_{\text{hc}}(\text{O}_2)^{(d)}$        |
| Formation of $\text{As}_2\text{O}_3$ :                                                                                    |                                                 |
| $2\text{As}(\text{s}, 298) + 3/2\text{O}_2(\text{g}, 298) \rightarrow \text{As}_2\text{O}_3(\text{s}, 298)$               | $\Delta H_f^\circ(\text{As}_2\text{O}_3)$       |
| $\Delta H_f^\circ(\text{arsenolite}, \text{As}_2\text{O}_3) = -\Delta H_1 + \Delta H_2 + \Delta H_3 - \Delta H_4$         |                                                 |

<sup>a</sup> "s", "g" and "soln" are for "solid", "gas" and "in solution" (in sodium molybdate) respectively.

<sup>b</sup>  $\Delta H_{\text{ds}}$ ,  $\Delta H_f^\circ$  and  $\Delta H_{\text{hc}}$  are respectively the drop solution enthalpy, standard enthalpy of formation and heat content.

<sup>c</sup> SGTE (1999).

<sup>d</sup> Robie and Hemingway (1995).

For our calculations, we used for the enthalpy of formation ( $\Delta H_f^0$ ) of  $\text{As}_2\text{O}_5$  the value -926 kJ/mol, which comes from a self-consistent and compatible thermodynamic dataset (SGTE, 1999). For the same compound other authors reported -925.5 kJ/mol (Wagman et al., 1968) and -924.87 kJ/mol (Wagman et al., 1982) respectively, values which are close to the one we used. This two values come from an earlier (1964) but no reference is given. Later compilations of thermodynamic data (Barin, 1995; Binnewies and Milke, 2002) for  $\text{As}_2\text{O}_5$  all refer to the same published value of Wagman et al. (1982).

Using the thermodynamic cycle (Table 1), measured, and literature (SGTE, 1999) thermodynamic data, we calculated the enthalpy of formation of arsenolite to be  $-652.6 \pm 2.7$  kJ/mol. This new measurement compares well with data available in literature -653.9 kJ/mol (SGTE, 1999). For the enthalpy of formation of arsenolite other authors give -657.27 kJ/mol (Nordstrom and Archer, 2003),  $-657.0 \pm 1.7$  kJ/mol (Robie and Hemingway, 1995), and -656.97 kJ/mol (Wagman et al., 1968). All of these data can be traced back to Wagman et al. (1982) with slightly modification, like rounding the decimals, giving estimated uncertainties or using weighted least-squares multiple regression on multiple thermodynamic measurements. We consider that the value -653.9 kJ/mol (SGTE, 1999) for enthalpy of formation of arsenolite is reliable, because it comes from a self-consistent and compatible thermodynamic dataset.


The enthalpy of formation of the synthetic Pb-As, Pb-Cu and Pb-Zn jarosites,  $\Delta H_f^\circ$ , was determined from the enthalpy of drop solution,  $\Delta H_{\text{ds}}$ , using the thermodynamic cycles given in Tables 2, 3, and 4. These cycles involves the enthalpy of drop solution of lead carbonate  $\text{PbCO}_3$  (Forray et al., 2010), ZnO, and CuO as well as other thermodynamic data taken from the literature (Drouet and Navrotsky, 2003; Majzlan et al., 2002; Nordstrom and Archer, 2003; Robie and Hemingway, 1995; SGTE, 1999) and listed in Table 5. Application of these thermodynamic cycles leads to the heat of formation, from the elements ( $\Delta H_f^\circ$ ) -  $3691.2 \pm 8.6$  kJ/mol for the synthetic Pb-As jarosite,  $-3653.6 \pm 8.2$  kJ/mol for the synthetic Pb-Cu jarosite and  $-3669.4 \pm 8.4$  kJ/mol for the synthetic Pb-Zn jarosite. We included all the uncertainties (from chemical analysis and from thermodynamic data) to assess the error propagation through our calculations.

There are numerous methods for estimating the entropy of minerals (e.g. Helgeson et al., 1978; Holland, 1989; Latimer, 1951). These calculations are used mainly for silicates. Due to the lack of data for compounds not related to silicates, we could only use the method of Latimer (1951) to estimate the entropy for Pb-As, Pb-Cu and Pb-Zn jarosites. The third-law entropy is the sum of calorimetric entropy and the residual entropy. The later one is related to structural disorders, site-mixing, magnetic spin disorders and so on. The calorimetric entropy in most of the cases is the major contributor to the total entropy. Latimer's method estimates the entropies of solid inorganic compounds by taking into account the effects of mass, ionic charge, and ionic size. For  $\text{AsO}_4^{2-}$  and  $\text{H}_3\text{O}^+$  where no data either, but we calculated the entropy of  $\text{AsO}_4^{2-}$  using data on  $\text{CrO}_4^{2-}$  available in Latimer (1951), to estimate the bond strength, because the ionic radius in tetrahedral coordination of  $\text{Cr}^{5+}$  (0.485 Å) is close to the  $\text{As}^{5+}$  ionic radius (0.475 Å) in  $\text{AsO}_4^{2-}$ . Using the entropy values for loosely bound water to hydrated minerals and the entropy value for  $\text{OH}^-$ , both given by Latimer (1951), we calculated the entropy of  $\text{H}^+$  in water like structure. The entropy of  $\text{H}_3\text{O}^+$  was calculated using the entropy data of water (Table 6) and the determined value for  $\text{H}^+$ .

**Table 2.** Thermodynamic cycle for the determination of  $\Delta H_f^\circ$  of Pb-As jarosite.

| Reaction <sup>a</sup>                                                                                                                                                                                                                                                                                                                                                                                   | $\Delta H$ (kJ/mol) <sup>b</sup>                          |
|---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------|
| (1) $(\text{H}_3\text{O})_{0.68}\text{Pb}_{0.32}\text{Fe}_{2.86}(\text{SO}_4)_{1.69}(\text{AsO}_4)_{0.31}(\text{OH})_{5.59}(\text{H}_2\text{O})_{0.41}(\text{s}, 298) \rightarrow 0.32 \text{ PbO (soln, 973)} + 1.43 \text{ Fe}_2\text{O}_3 \text{ (soln, 973)} + 0.155 \text{ As}_2\text{O}_5 \text{ (soln, 973)} + 1.69 \text{ SO}_3 \text{ (soln, 973)} + 4.225 \text{ H}_2\text{O (g, 973)}$ ..... | $\Delta H_{\text{ds}}$ (Pb-As jarosite)                   |
| (2) $\text{PbCO}_3 \text{ (s, 298)} \rightarrow \text{PbO (soln, 973)} + \text{CO}_2 \text{ (g, 973)}$ .....                                                                                                                                                                                                                                                                                            | $\Delta H_{\text{ds}}$ (PbCO <sub>3</sub> )               |
| (3) $\text{Pb (s, 298)} + \text{C (s, 298)} + 3/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{PbCO}_3 \text{ (s, 298)}$ .....                                                                                                                                                                                                                                                                        | $\Delta H_f^\circ$ (PbCO <sub>3</sub> )                   |
| (4) $\text{CO}_2 \text{ (g, 298)} \rightarrow \text{CO}_2 \text{ (g, 973)}$ .....                                                                                                                                                                                                                                                                                                                       | $\Delta H_{\text{hc}}$ (CO <sub>2(g)</sub> )              |
| (5) $\text{C (s, 298)} + \text{O}_2 \text{ (g, 298)} \rightarrow \text{CO}_2 \text{ (g, 298)}$ .....                                                                                                                                                                                                                                                                                                    | $\Delta H_f^\circ$ (CO <sub>2(g)</sub> )                  |
| (6) $\alpha\text{-Fe}_2\text{O}_3 \text{ (s, 298)} \rightarrow \text{Fe}_2\text{O}_3 \text{ (soln, 973)}$ .....                                                                                                                                                                                                                                                                                         | $\Delta H_{\text{ds}}$ ( $\alpha\text{Fe}_2\text{O}_3$ )  |
| (7) $2 \text{ Fe (s, 298)} + 3/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \alpha\text{Fe}_2\text{O}_3 \text{ (s, 298)}$ .....                                                                                                                                                                                                                                                                           | $\Delta H_f^\circ$ (Fe <sub>2</sub> O <sub>3</sub> )      |
| (8) $\text{As}_2\text{O}_5 \text{ (s, 298)} \rightarrow \text{As}_2\text{O}_5 \text{ (soln, 973)}$ .....                                                                                                                                                                                                                                                                                                | $\Delta H_{\text{ds}}$ (As <sub>2</sub> O <sub>5</sub> )  |
| (9) $2 \text{ As (s, 298)} + 5/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{As}_2\text{O}_5 \text{ (s, 298)}$ .....                                                                                                                                                                                                                                                                                 | $\Delta H_f^\circ$ (As <sub>2</sub> O <sub>5</sub> )      |
| (10) $\text{SO}_3 \text{ (g, 298)} \rightarrow \text{SO}_3 \text{ (soln, 973)}$ .....                                                                                                                                                                                                                                                                                                                   | $\Delta H_{\text{ds}}$ (SO <sub>3(g)</sub> ) <sup>c</sup> |
| (11) $\text{S (s, 298)} + 3/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{SO}_3 \text{ (g, 298)}$ .....                                                                                                                                                                                                                                                                                              | $\Delta H_f^\circ$ (SO <sub>3(g)</sub> )                  |
| (12) $\text{H}_2\text{O (g, 298)} \rightarrow \text{H}_2\text{O (g, 973)}$ .....                                                                                                                                                                                                                                                                                                                        | $\Delta H_{\text{hc}}$ (H <sub>2</sub> O <sub>(g)</sub> ) |
| (13) $\text{H}_2 \text{ (g, 298)} + 1/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{H}_2\text{O (g, 298)}$ .....                                                                                                                                                                                                                                                                                     | $\Delta H_f^\circ$ (H <sub>2</sub> O <sub>(g)</sub> )     |

Formation of Pb-As jarosite:



$$\Delta H_f^\circ \text{ (Pb-As jarosite)} = -\Delta H_1 + 0.32 \Delta H_2 + 0.32 \Delta H_3 - 0.32 \Delta H_4 - 0.32 \Delta H_5 + 1.43 \Delta H_6 + 1.43 \Delta H_7 \\ + 0.155 \Delta H_8 + 0.155 \Delta H_9 + 1.69 \Delta H_{10} + 1.69 \Delta H_{11} + 4.225 \Delta H_{12} + 4.225 \Delta H_{13}$$

<sup>a</sup> "s", "g" and "soln" are for "solid", "gas" and "in solution" (in sodium molybdate).


<sup>b</sup>  $\Delta H_{\text{ds}}$ ,  $\Delta H_f^\circ$  and  $\Delta H_{\text{hc}}$  are respectively the drop solution enthalpy, standard enthalpy of formation and heat content.

<sup>c</sup>  $\Delta H_{\text{ds}}$  (SO<sub>3(g)</sub>) as determined by Majzlan et al. (2002).

**Table 3.** Thermodynamic cycle for the determination of  $\Delta H_f^\circ$  of Pb-Cu jarosite.

| Reaction <sup>a</sup>                                                                                                                                                                                                                                                                                                                                                   | $\Delta H$ (kJ/mol) <sup>b</sup>                          |
|-------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------|
| (1) $(\text{H}_3\text{O})_{0.67}\text{Pb}_{0.33}\text{Fe}_{2.71}\text{Cu}_{0.25}(\text{SO}_4)_2(\text{OH})_{5.96}(\text{H}_2\text{O})_{0.04}(\text{s}, 298) \rightarrow 0.33 \text{ PbO (soln, 973)} + 1.355 \text{ Fe}_2\text{O}_3 \text{ (soln, 973)} + 0.25 \text{ CuO (soln, 973)} + 2 \text{ SO}_3 \text{ (soln, 973)} + 4.025 \text{ H}_2\text{O (g, 973)}$ ..... | $\Delta H_{\text{ds}}$ (Pb-Cu jarosite)                   |
| (2) $\text{PbCO}_3 \text{ (s, 298)} \rightarrow \text{PbO (soln, 973)} + \text{CO}_2 \text{ (g, 973)}$ .....                                                                                                                                                                                                                                                            | $\Delta H_{\text{ds}}$ (PbCO <sub>3</sub> )               |
| (3) $\text{Pb (s, 298)} + \text{C (s, 298)} + 3/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{PbCO}_3 \text{ (s, 298)}$ .....                                                                                                                                                                                                                                        | $\Delta H_f^\circ$ (PbCO <sub>3</sub> )                   |
| (4) $\text{CO}_2 \text{ (g, 298)} \rightarrow \text{CO}_2 \text{ (g, 973)}$ .....                                                                                                                                                                                                                                                                                       | $\Delta H_{\text{hc}}$ (CO <sub>2(g)</sub> )              |
| (5) $\text{C (s, 298)} + \text{O}_2 \text{ (g, 298)} \rightarrow \text{CO}_2 \text{ (g, 298)}$ .....                                                                                                                                                                                                                                                                    | $\Delta H_f^\circ$ (CO <sub>2(g)</sub> )                  |
| (6) $\alpha\text{-Fe}_2\text{O}_3 \text{ (s, 298)} \rightarrow \text{Fe}_2\text{O}_3 \text{ (soln, 973)}$ .....                                                                                                                                                                                                                                                         | $\Delta H_{\text{ds}}$ ( $\alpha\text{Fe}_2\text{O}_3$ )  |
| (7) $2 \text{ Fe (s, 298)} + 3/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \alpha\text{Fe}_2\text{O}_3 \text{ (s, 298)}$ .....                                                                                                                                                                                                                                           | $\Delta H_f^\circ$ (Fe <sub>2</sub> O <sub>3</sub> )      |
| (8) $\text{CuO (s, 298)} \rightarrow \text{CuO (soln, 973)}$ .....                                                                                                                                                                                                                                                                                                      | $\Delta H_{\text{ds}}$ (CuO)                              |
| (9) $\text{Cu (s, 298)} + 1/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{CuO (s, 298)}$ .....                                                                                                                                                                                                                                                                       | $\Delta H_f^\circ$ (CuO)                                  |
| (10) $\text{SO}_3 \text{ (g, 298)} \rightarrow \text{SO}_3 \text{ (soln, 973)}$ .....                                                                                                                                                                                                                                                                                   | $\Delta H_{\text{ds}}$ (SO <sub>3(g)</sub> ) <sup>c</sup> |
| (11) $\text{S (s, 298)} + 3/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{SO}_3 \text{ (g, 298)}$ .....                                                                                                                                                                                                                                                              | $\Delta H_f^\circ$ (SO <sub>3(g)</sub> )                  |
| (12) $\text{H}_2\text{O (g, 298)} \rightarrow \text{H}_2\text{O (g, 973)}$ .....                                                                                                                                                                                                                                                                                        | $\Delta H_{\text{hc}}$ (H <sub>2</sub> O <sub>(g)</sub> ) |
| (13) $\text{H}_2 \text{ (g, 298)} + 1/2 \text{ O}_2 \text{ (g, 298)} \rightarrow \text{H}_2\text{O (g, 298)}$ .....                                                                                                                                                                                                                                                     | $\Delta H_f^\circ$ (H <sub>2</sub> O <sub>(g)</sub> )     |

Formation of Pb-Cu jarosite:



$$\Delta H_f^\circ \text{ (Pb-Cu jarosite)} = -\Delta H_1 + 0.33 \Delta H_2 + 0.33 \Delta H_3 - 0.33 \Delta H_4 - 0.33 \Delta H_5 + 1.355 \Delta H_6 + 1.355 \Delta H_7 \\ + 0.25 \Delta H_8 + 0.25 \Delta H_9 + 2 \Delta H_{10} + 2 \Delta H_{11} + 4.025 \Delta H_{12} + 4.025 \Delta H_{13}$$

<sup>a</sup> "s", "g" and "soln" are for "solid", "gas" and "in solution" (in sodium molybdate).


<sup>b</sup>  $\Delta H_{\text{ds}}$ ,  $\Delta H_f^\circ$  and  $\Delta H_{\text{hc}}$  are respectively the drop solution enthalpy, standard enthalpy of formation and heat content.

<sup>c</sup>  $\Delta H_{\text{ds}}$  (SO<sub>3(g)</sub>) as determined by Majzlan et al. (2002).

**Table 4.** Thermodynamic cycle for the determination of  $\Delta H_f^\circ$  of Pb-Zn jarosite.

| Reaction <sup>a</sup>                                                                                                                                                                                                                                                                                                                                                                | $\Delta H$ (kJ/mol) <sup>b</sup>                          |
|--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|-----------------------------------------------------------|
| (1) $(\text{H}_3\text{O})_{0.57} \text{Pb}_{0.43} \text{Fe}_{2.70} \text{Zn}_{0.21} (\text{SO}_4)_2 (\text{OH})_{5.95} (\text{H}_2\text{O})_{0.05} (\text{s}, 298) \rightarrow 0.43 \text{PbO} (\text{soln}, 973) + 1.35 \text{Fe}_2\text{O}_3 (\text{soln}, 973) + 0.21 \text{ZnO} (\text{soln}, 973) + 2 \text{SO}_3 (\text{soln}, 973) + 3.88 \text{H}_2\text{O} (\text{g}, 973)$ | $\Delta H_{\text{ds}}$ (Pb-Zn jarosite)                   |
| (2) $\text{PbCO}_3 (\text{s}, 298) \rightarrow \text{PbO} (\text{soln}, 973) + \text{CO}_2 (\text{g}, 973)$                                                                                                                                                                                                                                                                          | $\Delta H_{\text{ds}}$ (PbCO <sub>3</sub> )               |
| (3) $\text{Pb} (\text{s}, 298) + \text{C} (\text{s}, 298) + 3/2 \text{O}_2 (\text{g}, 298) \rightarrow \text{PbCO}_3 (\text{s}, 298)$                                                                                                                                                                                                                                                | $\Delta H_f^\circ$ (PbCO <sub>3</sub> )                   |
| (4) $\text{CO}_2 (\text{g}, 298) \rightarrow \text{CO}_2 (\text{g}, 973)$                                                                                                                                                                                                                                                                                                            | $\Delta H_{\text{hc}}$ (CO <sub>2(g)</sub> )              |
| (5) $\text{C} (\text{s}, 298) + \text{O}_2 (\text{g}, 298) \rightarrow \text{CO}_2 (\text{g}, 298)$                                                                                                                                                                                                                                                                                  | $\Delta H_f^\circ$ (CO <sub>2(g)</sub> )                  |
| (6) $\alpha\text{-Fe}_2\text{O}_3 (\text{s}, 298) \rightarrow \text{Fe}_2\text{O}_3 (\text{soln}, 973)$                                                                                                                                                                                                                                                                              | $\Delta H_{\text{ds}}$ ( $\alpha\text{Fe}_2\text{O}_3$ )  |
| (7) $2 \text{Fe} (\text{s}, 298) + 3/2 \text{O}_2 (\text{g}, 298) \rightarrow \alpha\text{Fe}_2\text{O}_3 (\text{s}, 298)$                                                                                                                                                                                                                                                           | $\Delta H_f^\circ$ (Fe <sub>2</sub> O <sub>3</sub> )      |
| (8) $\text{ZnO} (\text{s}, 298) \rightarrow \text{ZnO} (\text{soln}, 973)$                                                                                                                                                                                                                                                                                                           | $\Delta H_{\text{ds}}$ (ZnO)                              |
| (9) $\text{Zn} (\text{s}, 298) + 1/2 \text{O}_2 (\text{g}, 298) \rightarrow \text{ZnO} (\text{s}, 298)$                                                                                                                                                                                                                                                                              | $\Delta H_f^\circ$ (ZnO)                                  |
| (10) $\text{SO}_3 (\text{g}, 298) \rightarrow \text{SO}_3 (\text{soln}, 973)$                                                                                                                                                                                                                                                                                                        | $\Delta H_{\text{ds}}$ (SO <sub>3(g)</sub> ) <sup>c</sup> |
| (11) $\text{S} (\text{s}, 298) + 3/2 \text{O}_2 (\text{g}, 298) \rightarrow \text{SO}_3 (\text{g}, 298)$                                                                                                                                                                                                                                                                             | $\Delta H_f^\circ$ (SO <sub>3(g)</sub> )                  |
| (12) $\text{H}_2\text{O} (\text{g}, 298) \rightarrow \text{H}_2\text{O} (\text{g}, 973)$                                                                                                                                                                                                                                                                                             | $\Delta H_{\text{hc}}$ (H <sub>2</sub> O <sub>(g)</sub> ) |
| (13) $\text{H}_2 (\text{g}, 298) + 1/2 \text{O}_2 (\text{g}, 298) \rightarrow \text{H}_2\text{O} (\text{g}, 298)$                                                                                                                                                                                                                                                                    | $\Delta H_f^\circ$ (H <sub>2</sub> O <sub>(g)</sub> )     |

Formation of Pb-Zn jarosite:



$$\Delta H_f^\circ (\text{Pb-Zn jarosite}) = -\Delta H_1 + 0.43 \Delta H_2 + 0.43 \Delta H_3 - 0.43 \Delta H_4 - 0.43 \Delta H_5 + 1.35 \Delta H_6 + 1.35 \Delta H_7 + 0.21 \Delta H_8 + 0.21 \Delta H_9 + 2 \Delta H_{10} + 2 \Delta H_{11} + 3.88 \Delta H_{12} + 3.88 \Delta H_{13}$$

<sup>a</sup> "s", "g" and "soln" are for "solid", "gas" and "in solution" (in sodium molybdate).

<sup>b</sup>  $\Delta H_{\text{ds}}$ ,  $\Delta H_f^\circ$  and  $\Delta H_{\text{hc}}$  are respectively the drop solution enthalpy, standard enthalpy of formation and heat content.

<sup>c</sup>  $\Delta H_{\text{ds}}$  (SO<sub>3(g)</sub>) as determined by Majzlan et al. (2002).

**Table 5.** Thermodynamic data used in this work.

| Compound                                                                                                                                                                         | $\Delta H_{\text{hc}}$ (kJ/mol) | $\Delta H_{\text{ds}}$ (kJ/mol) | $\Delta H_f^\circ$ , 298 K (kJ/mol) | $\Delta G_f^\circ$ , 298 K (kJ/mol) |
|----------------------------------------------------------------------------------------------------------------------------------------------------------------------------------|---------------------------------|---------------------------------|-------------------------------------|-------------------------------------|
| Pb <sup>2+</sup>                                                                                                                                                                 |                                 |                                 |                                     | -24.2 ± 0.2 <sup>c</sup>            |
| Zn <sup>2+</sup>                                                                                                                                                                 |                                 |                                 |                                     | -147.3 ± 0.2 <sup>c</sup>           |
| Fe <sup>3+</sup>                                                                                                                                                                 |                                 |                                 |                                     | -16.7 ± 2.0 <sup>c</sup>            |
| Cu <sup>2+</sup>                                                                                                                                                                 |                                 |                                 |                                     | 65.1 ± 0.1 <sup>c</sup>             |
| PbCO <sub>3</sub>                                                                                                                                                                |                                 | 101.4 ± 0.8 <sup>a</sup>        | -699.2 ± 1.2 <sup>c</sup>           |                                     |
| $\alpha\text{-Fe}_2\text{O}_3$                                                                                                                                                   |                                 | 95.0 ± 1.8 <sup>b</sup>         | -826.2 ± 1.3 <sup>c</sup>           |                                     |
| CuO                                                                                                                                                                              |                                 | 41.9 ± 0.6 (11) <sup>*</sup>    | -156.1 ± 2.0 <sup>c</sup>           |                                     |
| ZnO                                                                                                                                                                              |                                 | 19.4 ± 0.7 (18) <sup>*</sup>    | -350.5 ± 0.3 <sup>c</sup>           |                                     |
| As <sub>2</sub> O <sub>3</sub>                                                                                                                                                   |                                 | -218.5 ± 2.6 (31) <sup>*</sup>  | -653.9 <sup>e</sup>                 |                                     |
| As <sub>2</sub> O <sub>5</sub>                                                                                                                                                   |                                 | 76.7 ± 0.8 (11) <sup>*</sup>    | -926 <sup>e</sup>                   |                                     |
| AsO <sub>4</sub> <sup>3-</sup> (aq)                                                                                                                                              |                                 |                                 |                                     | -646.36 <sup>f</sup>                |
| SO <sub>3(g)</sub>                                                                                                                                                               |                                 | -205.8 ± 3.7 <sup>d</sup>       | -395.7 ± 0.7 <sup>c</sup>           |                                     |
| SO <sub>4</sub> <sup>2-</sup> (aq)                                                                                                                                               |                                 |                                 |                                     | -744 ± 0.4 <sup>c</sup>             |
| CO <sub>2(g)</sub>                                                                                                                                                               | 31.94 ± 0.0                     |                                 | -393.5 ± 0.1 <sup>c</sup>           |                                     |
| H <sub>2</sub> O <sub>(g)</sub>                                                                                                                                                  | 24.89 ± 0.0                     |                                 | -241.8 ± 0.0 <sup>c</sup>           |                                     |
| H <sub>2</sub> O <sub>(l)</sub>                                                                                                                                                  |                                 |                                 |                                     | -237.1 ± 0.1 <sup>c</sup>           |
| O <sub>2(g)</sub>                                                                                                                                                                | 21.8 ± 0.0                      |                                 |                                     |                                     |
| <b>Pb-As jarosite:</b> $(\text{H}_3\text{O})_{0.68} \text{Pb}_{0.32} \text{Fe}_{2.86} (\text{SO}_4)_{1.69} (\text{AsO}_4)_{0.31} (\text{OH})_{5.59} (\text{H}_2\text{O})_{0.41}$ |                                 |                                 | 505.4 ± 4.8 (12) <sup>*</sup>       |                                     |
| <b>Pb-Cu jarosite:</b> $(\text{H}_3\text{O})_{0.67} \text{Pb}_{0.33} \text{Fe}_{2.71} \text{Cu}_{0.25} (\text{SO}_4)_2 (\text{OH})_{5.96} (\text{H}_2\text{O})_{0.04}$           |                                 |                                 | 480.3 ± 1.2 (12) <sup>*</sup>       |                                     |
| <b>Pb-Zn jarosite:</b> $(\text{H}_3\text{O})_{0.57} \text{Pb}_{0.43} \text{Fe}_{2.70} \text{Zn}_{0.21} (\text{SO}_4)_2 (\text{OH})_{5.95} (\text{H}_2\text{O})_{0.05}$           |                                 |                                 | 466.6 ± 2.0 (16) <sup>*</sup>       |                                     |

<sup>\*</sup>Uncertainties are two standard deviations of the mean. Parentheses are the numbers of experiments performed.

<sup>a</sup> Forray et al. (2010), <sup>b</sup> Drouet and Navrotsky (2003), <sup>c</sup> Robie and Hemingway (1995).

<sup>d</sup> Majzlan et al. (2002), <sup>e</sup> SGTE (1999), <sup>f</sup> Nordstrom and Archer (2003).

**Table 6.** Entropy values for different compounds at 298.15 K.

| Compound                       | $S^{\circ}$ (J·mol <sup>-1</sup> K <sup>-1</sup> ) |
|--------------------------------|----------------------------------------------------|
| H <sub>3</sub> O <sup>+</sup>  | 56.90(2) <sup>2</sup>                              |
| Pb                             | 64.85(2) <sup>1</sup>                              |
| Fe                             | 43.51(4) <sup>1</sup>                              |
| Cu                             | 45.18(7) <sup>1</sup>                              |
| S                              | 35.56(4) <sup>1</sup>                              |
| Zn                             | 45.60(6) <sup>1</sup>                              |
| K                              | 38.49(3) <sup>1</sup>                              |
| Na                             | 31.38(0) <sup>1</sup>                              |
| Cr                             | 42.67(7) <sup>1</sup>                              |
| H <sub>2</sub> O               | 39.32(9) <sup>1</sup>                              |
| OH <sup>-</sup>                | 18.82(8) <sup>1</sup>                              |
| SO <sub>4</sub> <sup>2-</sup>  | 71.96(5) <sup>1</sup>                              |
| CrO <sub>4</sub> <sup>2-</sup> | 87.86(4) <sup>1</sup>                              |
| AsO <sub>4</sub> <sup>2-</sup> | 93.09(4) <sup>2</sup>                              |
| Pb-Cu jarosite                 | 455.7 <sup>2</sup>                                 |
| Pb-Zn jarosite                 | 446.5 <sup>2</sup>                                 |
| Pb-As jarosite                 | 445.3 <sup>2</sup>                                 |

<sup>1</sup> Latimer (1951).<sup>2</sup> calculated

In order to test the validity of entropy calculations, we calculated the entropy values for well characterized jarosites from the literature, for which experimentally determined entropy data were available. The entropy of (H<sub>3</sub>O)<sub>0.91</sub>Fe<sub>2.91</sub>(SO<sub>4</sub>)<sub>2</sub>(OH)<sub>5.64</sub>(H<sub>2</sub>O)<sub>0.18</sub> was determined experimentally to be 438.9 ± 0.7 J/mol·K (Majzlan et al., 2004), using adiabatic and semi-adiabatic calorimetry. For the same mineral, applying the method of Latimer (1951), using the data from Table 6, we obtained the value 435.6 J/mol·K. Furthermore, for K<sub>0.92</sub>(H<sub>3</sub>O)<sub>0.08</sub>Fe<sub>2.97</sub>(SO<sub>4</sub>)<sub>2</sub>(OH)<sub>5.90</sub>(H<sub>2</sub>O)<sub>0.10</sub> and Na<sub>0.95</sub>(H<sub>3</sub>O)<sub>0.05</sub>Fe<sub>3.00</sub>(SO<sub>4</sub>)<sub>2</sub>(OH)<sub>6.00</sub> jarosites, Majzlan et al. (2010) determined experimentally the entropy 427.4 ± 0.7 and 436.4 ± 4.4 J/mol·K. The entropy estimate for this two jarosites, using the Latimer (1951) method was 428.2 and 420.1 J/mol·K. The latter value showed the biggest difference between experimental and estimated value of 16.3 J/mol·K, but the previous differences are between 0.8 to 3.3 J/mol·K. This Na-jarosite is almost a pure stoichiometric sodium jarosite with only small substitution of Na with H<sub>3</sub>O<sup>+</sup> and has the unit cell c axis shorter than the other jarosites. These chemical and structural changes may alter the bonding strength and affect the calculated entropy. For simpler compounds, Latimer's method gives an error of 4.2 to 8.4 J/mol·K, but certainly higher for more complex compounds. Considering these entropy values, an uncertainty of ± 10 J/mol·K could be considered for future calculations. At ambient temperature, this uncertainty ion entropy gives an uncertainty of the Gibbs free energy of only ± 3 kJ/mol.

Using the method of Latimer (1951), we calculated the entropy of Pb-As, Pb-Cu and Pb-Zn jarosites as 455.7 ± 10, 446.5 ± 10 and 445.3 ± 10 J/mol·K. This is the lattice vibrational entropy that does not include configurational or magnetic effects. The third-law entropy is the sum of calorimetric entropy and the residual entropy. The latter one is related to structural disorder, site-mixing, magnetic spin disorders and so on. The calorimetric entropy in most of the cases is the major contributor to the total entropy. In case of our jarosites, the configurational entropy is not a significant contributor to the total entropy. This make us confident that the error we introduce in our calculation are small compared to the overall error, calculated using error propagation. These give an entropy of formation  $\Delta S_f^{\circ}$  of -1765.6 ± 10, -1751.5 ± 10 and -1730.1 ± 10 J/mol·K, respectively. Applying the equation defining the Gibbs free energy,  $\Delta G_f^{\circ} = \Delta H_f^{\circ} - T \Delta S_f^{\circ}$ , the Gibbs free energy of formation from elements for Pb-As, Pb-Cu and Pb-Zn jarosites are listed in Table 7.

The measured compounds do not have stoichiometric end-member compositions but their thermodynamic data may nevertheless be useful for geochemical calculations. In nature end-members of the alunite group minerals are rare. More often, the minerals are nonstoichiometric and solid solutions between the end- members form; some authors call them near-end-members (Desborough et al., 2010). Some crystals contain fine-scale chemical zoning (Desborough et al., 2010; Papike et al., 2006). Considering

this complexity, the thermodynamic data for the synthetic jarosites measured in this work may be applicable to real minerals.


**Table 7.** Measured and calculated thermodynamic data.

| Compound*      | $\Delta G_f^0$ (kJ/mol) | $\Delta H_f^0$ (kJ/mol) | $\Delta S_f^0$ (J/mol·K) | $\log K_{sp}$ (at 298K) |
|----------------|-------------------------|-------------------------|--------------------------|-------------------------|
| Pb-As jarosite | $-3164.8 \pm 9.1$       | $-3691.2 \pm 8.6$       | $-1765.6 \pm 10.0$       | $-13.94 \pm 1.89$       |
| Pb-Cu jarosite | $-3131.4 \pm 8.7$       | $-3653.6 \pm 8.2$       | $-1751.5 \pm 10.0$       | $-4.38 \pm 1.81$        |
| Pb-Zn jarosite | $-3153.6 \pm 8.9$       | $-3669.4 \pm 8.4$       | $-1730.1 \pm 10.0$       | $-3.75 \pm 1.80$        |

\* For Pb-As jarosite, Pb-Cu jarosite, and Pb-Zn jarosite formula see Table 5.

These are the first calorimetric data on beaverite and beudantite like compounds. Roussel et al. (2000) estimated the Gibbs free energy of formation from elements for beudantite as  $-727.5$  kcal/mol ( $-3043.9$  kJ/mol) using thermodynamic data from Kashkay et al. (1975). This value gives a solubility product ( $K_{sp}$ ) for beudantite of  $10^{-15}$  which is higher than our  $\approx 10^{-12}$  value.

Gaboreau and Vieillard (2004) developed a method to estimate the Gibbs free energy of formation of minerals in the alunite supergroup. They estimated the  $\Delta G_f^0$  of beudantite to be  $-3055.6$  kJ/mol, but the mineral formula is listed as  $PbFe_3(AsO_4)_2(OH)_5H_2O$ . If we use this value and the chemical formula, the calculated solubility product  $K_{sp}$  will be  $10^{-29}$  or  $\log_{10}K_{sp} = -29$ . This value is rather high in magnitude compared to  $\log_{10}K_{sp}$  for major jarosites, which have values between  $-8.36$  and  $-12.50$ .

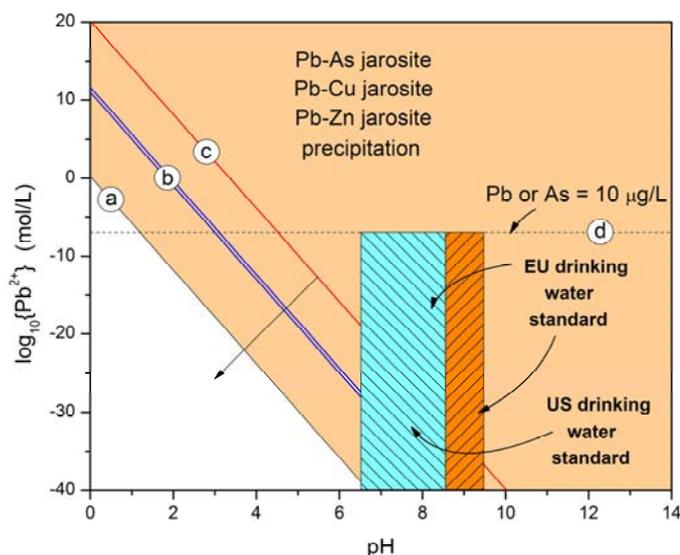

**Fig. 4.** Stability of Pb-As, Pb-Cu, and Pb-Zn jarosites as function of pH and lead activity; a – stability boundary for Pb-As jarosite; b – stability boundary for Pb-Cu, and Pb-Zn jarosite; c – stability boundary for Pb-As jarosite at very low Fe,  $SO_4$  and As activity (10 ppb each); d – maximum level of Pb and As in drinking water (US and EU standard). For boundary (a) and (b), the species activities where:  $Fe^{3+} 3.22 \cdot 10^{-3}$  mol/L,  $As^{5+} 1.33 \cdot 10^{-7}$  mol/L and  $SO_4^{2-} 1.56 \cdot 10^{-2}$  mol/L.

Using our data on Pb-As, Pb-Cu, and Pb-Zn jarosites, we calculated the  $\log_{10}\{Pb^{2+}\} - pH$  diagram for the solubility of these minerals (Fig. 4). In this figure, the hatched zone represents the drinking water standard boundary for US (EPA, National Secondary Drinking Water Regulations) and EU (Council Directive 98/83/EC), with respect to pH, Pb and As content. From this graph we can see that if there is an increase in dissolved arsenic in the water the stability boundary for Pb-As jarosite (Fig. 4. line (c)) shifts toward line (a), as indicated by the arrow. Pb-As jarosite precipitation (above line (a) in Fig. 4) controls the  $Pb^{2+}$  and  $As^{5+}$  content in the water. As the graph shows, Pb-Cu and Pb-Zn jarosites have very similar solubility products and their stability lines overlap. In rare cases, the  $Pb^{2+}$  and  $As^{5+}$  content in the water in equilibrium with these phases would exceed the drinking water standard but only at low pH ( $<1.5$ ). This indicates that Pb-As jarosite can be a candidate for immobilization of arsenic and  $Pb^{2+}$ . Kocourková et al (2011) even consider it as a “long-term” option for arsenic immobilization. The research of Kingsbury and Hartley (1960) on minerals related to mine sites, mentions the transformation of carminite to beudantite, and the beudantite

may transform to plumbojarosite or beaverite. Using the new thermodynamic data, the negative value of the Gibbs free energy of the transformation reaction from Pb-As jarosite to plumbojarosite confirms that Pb-As jarosite can transform to plumbojarosite.

### 3.3. Conclusions

The enthalpy of formation from the elements of synthetic Pb-As, Pb-Cu and Pb-Zn jarosites were determined by high temperature oxide melt solution calorimetry. This is the first direct measurement of the heat of formation for a beudantite and beaverite like compound. The entropies of these compounds were estimated using the method of Latimer (1951). The data should prove useful for geochemical and environmental calculations. Examples of the calculation of  $\log_{10}\{Pb^{2+}\} - pH$  diagram and solubility product were given for the studied compounds. The dissolution/transformation reactions of arsenic containing jarosites are much more complex. A recent study (Kendall et al., 2013) indicates that arsenic containing jarosites have incongruent dissolution. Future work is needed to understand the processes between arsenic and jarosite type minerals.

### Acknowledgments

This work was funded through U.S. Department of Energy (grant DEFG02-97ER14749) to A. Navrotsky and through the UK Engineering and Physical Sciences Research Council (EPSRC) studentship award (number 309778) to A.M.L. Smith. We thank A.S. Wills for the GSAS refinement of the original synthetic plumbojarosite, C. Jones and A. Ball for help with SEM analysis and photography, G. Jones and V. Din for assistance with geochemical analysis, and I. Wood for expert help with the XRD analysis.

### References

- Alcobé, X., Bassas, J., Tarruella, I., Roca, A., Viñals, J., 2001. Structural characterization of synthetic beudantite-type phases by Rietveld refinement, EPDIC 7: European Powder Diffraction, pp. 671-676.
- Barin, I., 1995. Thermochemical data of pure substances. Wiley-VCH Verlag.
- Baron, D., Palmer, C.D., 1996. Solubility of jarosite at 4-35 °C. *Geochim. Cosmochim. Acta* 60, 185-195.
- Bigham, J.M., Nordstrom, D.K., 2000. Iron and aluminum hydroxysulfates from acid sulfate waters, in: Alpers, C.N., Jambor, J.L., Nordstrom, D.K. (Eds.), *Sulfate Minerals: Crystallography, Geochemistry, and Environmental Significance. Reviews in Mineralogy and Geochemistry*, pp. 351-403.
- Binnewies, M., Milke, E., 2002. Thermochemical data of elements and compounds. Wiley-VCH Verlag.
- Brophy, G.P., Sheridan, M.F., 1965. Sulfate studies IV: the jarosite–natrojarosite–hydronium jarosite solid solution series. *Am. Mineral.* 50, 1595–1607.
- Brunauer, S., Emmett, P.H., Teller, E., 1938. Adsorption of gases in multimolecular layers. *American Chemical Society Journal* 60, 309-319.
- Chiang, K.Y., Lin, K.C., Lin, S.C., Chang, T.-K., Wang, M.K., 2010. Arsenic and lead (beudantite) contamination of agricultural rice soils in the Guandu Plain of northern Taiwan. *J. Hazard. Mater.* 181, 1066-1071.
- Desborough, G.A., Smith, K.S., Lowers, H.A., Swayze, G.A., Hammarstrom, J.M., Diehl, S.F., Leinz, R.W., Driscoll, R.L., 2010. Mineralogical and chemical characteristics of some natural jarosites. *Geochim. Cosmochim. Acta* 74, 1041-1056.
- Dill, H.G., Melcher, F., Kaufhold, S., Techmer, A., Weber, B., Bäuml, W., 2010. Post-miocene and bronze-age supergene Cu–Pb arsenate – humate – oxalate – carbonate mineralization at Mega Livadi, Serifos, Greece. *Can. Mineral.* 48, 163-181.
- Drouet, C., Navrotsky, A., 2003. Synthesis, characterisation and thermochemistry of K-Na-H<sub>2</sub>O jarosites. *Geochim. Cosmochim. Acta* 67, 2063-2076.
- Dutrizac, J.E., Dinardo, O., 1983. The co-precipitation of copper and zinc with lead jarosite. *Hydrometallurgy* 11, 61-78.
- Dutrizac, J.E., Jambor, J.L., 2000. Jarosite and their application in hydrometallurgy, in: Alpers, C.N., Jambor, J.L. (Eds.), *Sulfate minerals: crystallography, geochemistry and environmental significance. Mineralogical Society of America, Washington, DC*, pp. 405-452.

- Dutrizac, J.E., Kaiman, S., 1976. Synthesis and properties of jarosite-type compounds. *Can. Mineral.* 14, 151-158.
- Forray, F.L., Drouet, C., Navrotsky, A., 2005. Thermochemistry of yavapaiite  $KFe(SO_4)_2$ : Formation and decomposition. *Geochim. Cosmochim. Acta* 69, 2133-2140.
- Forray, F.L., Smith, A.M.L., Drouet, C., Navrotsky, A., Wright, K., Hudson-Edwards, K.A., Dubbin, W.E., 2010. Synthesis, characterization and thermochemistry of a Pb-jarosite. *Geochim. Cosmochim. Acta* 74, 215-224.
- Gaboreau, S., Vieillard, P., 2004. Prediction of Gibbs free energies of formation of minerals of the alunite supergroup. *Geochim. Cosmochim. Acta* 68, 3307-3316.
- Giuseppetti, G., Tadini, C., 1980. The crystal structure of osarizawaite. *Neues Jb Miner Monat*, 401-407.
- Grey, I.E., Mumme, W.G., Bordet, P., Mills, S.J., 2008. A new crystal-chemical variation of the alunite-type structure in monoclinic  $PbZn_{0.5}Fe_3(AsO_4)_2(OH)_6$ . *The Canadian Mineralogist* 46, 1355-1364.
- Hawthorne, F.C., Krivovichev, S.V., Burns, P.C., 2000. The crystal chemistry of sulfite minerals, in: Alpers, C.N., Jambor, J.L., Nordstrom, D.K. (Eds.), *Sulfate minerals: Crystallography, Geochemistry, and Environmental Significance. Reviews in Mineralogy and Geochemistry*, pp. 1-112.
- Helgeson, H.C., Delany, J., Bird, D.K., 1978. Summary and critique of the thermodynamic properties of rock-forming minerals. *Am. J. Sci.* 278A, 1-229.
- Herbstein, F.H., 2000. How precise are measurements of unit-cell dimensions from single crystals? *Acta Crystallographica Section B Structural Science* 56, 547-557.
- Holland, T.J.B., 1989. Dependence of entropy on volume for silicate and oxide minerals: A review and a predictive model. *Am. Mineral.* 74, 5-13.
- Hudson-Edwards, K.A., Smith, A.M.L., Dubbin, W.E., Bennett, A.J., Murphy, P.J., Wright, K., 2008. Comparison of the structures of natural and synthetic Pb-Cu-jarosite-type compounds. *Eur. J. Mineral.* 20, 241-252.
- Jambor, J.L., 1999. Nomenclature of the alunite supergroup. *Can. Mineral.* 37, 1323-1341.
- Jambor, J.L., Dutrizac, J.E., 1983. Beaverite-plumbojarosite solid solutions. *Can. Mineral.* 21, 101-113.
- Jambor, J.L., Dutrizac, J.E., 1985. The synthesis of beaverite. *Can. Mineral.* 23, 47-51.
- Kashkay, C.M., Borovskaya, Y.B., Babazade, M.A., 1975. Determination of  $DG^{\circ}_{f, 298}$  of synthetic jarosite and its sulfate analogues. *Geochem. Intl.* 1975, 115-121, translated from *Geokhimiya* 115, 778-784.
- Kendall, M.R., Madden, A.S., Elwood Madden, M.E., Hu, Q., 2013. Effects of arsenic incorporation on jarosite dissolution rates and reaction products. *Geochim. Cosmochim. Acta* 112, 192-207.
- Kingsbury, A.W.G., Hartley, J., 1960. Carminite and beudantite from the northern part of the Lake District and from Cornwall. *Mineralogical Magazine* 32, 423-432.
- Klingelhöfer, G., Morris, R.V., Bernhardt, B., Schröder, C., Rodionov, D.S., de Souza, P.A.J., Yen, A., Gellert, R., Evlanov, E.N., Zubkov, B., Foh, J., Bonnes, U., Kankleit, E., Gütlich, P., Ming, D.W., Renz, F., Wdowiak, T., Squyres, S.W., Arvidson, R.E., 2004. Jarosite and hematite at Meridiani Planum from Opportunity's mössbauer spectrometer. *Science* 306, 1740-1745.
- Kocourková, E., Sracek, O., Houzar, S., Cempírek, J., Losos, Z., Filip, J., Hršelová, P., 2011. Geochemical and mineralogical control on the mobility of arsenic in a waste rock pile at Dlouhá Ves, Czech Republic. *Journal of Geochemical Exploration* 110, 61-73.
- Kubisz, J., 1964. A study of minerals in the alunite-jarosite group. *Polska Akad. Nauk. Prace Geol.* 22, 1-93.
- Kubisz, J., 1970. Studies on synthetic alkali-hydronium jarosite. I. Synthesis of jarosite and natrojarosite. *Mineralogia Polonica* 1, 47-57.
- Larson, A.C., Von Dreele, R.B., 2000. General structure analysis system (GSAS). Los Alamos National Laboratory, p. 231 p.
- Latimer, W.M., 1951. Methods of Estimating the Entropies of Solid Compounds. *J. Am. Chem. Soc.* 73, 1480-1482.
- Le Bail, A., Duroy, H., Fourquet, J.L., 1988. Ab-initio structure determination of  $LiSbWO_6$  by X-ray powder diffraction. *Mater. Res. Bull.* 23, 447-452.
- Majzlan, J., Glasnák, P., Fisher, R., White, M., Johnson, M., Woodfield, B., Boerio-Goates, J., 2010. Heat capacity, entropy, and magnetic properties of jarosite-group compounds. *Phys. Chem. Miner.* 37, 635-651.
- Majzlan, J., Navrotsky, A., Neil, J.M., 2002. Energetics of anhydrite, barite, celestine, and anglesite: A high-temperature and differential scanning calorimetry study. *Geochim. Cosmochim. Acta* 66, 1839-1850.

- Majzlan, J., Navrotsky, A., Stevens, R., Boerio-Goates, J., Woodfield, B.F., Burns, P.C., Crawford, M.K., Amos, T.G., 2004. Thermodynamic properties, low-temperature heat capacity anomalies, and single crystal X-ray refinement of hydronium jarosite,  $(\text{H}_3\text{O})\text{Fe}_3(\text{OH})_6(\text{SO}_4)_2$ . *Phys. Chem. Miner.* 31, 518-531.
- McConchie, D., Clark, M., Genc-Fuhrman, H., 2006. Iron control technology, *Proc. Int. Symp. Iron Control Hydrometallurgy 3<sup>rd</sup> edition*, pp. 927-941.
- Navrotsky, A., 1977. Progress and new directions in high temperature calorimetry. *Phys Chem Minerals* 2, 89-104.
- Navrotsky, A., 1997. Progress and new directions in high temperature calorimetry revisited. *Phys Chem Minerals* 24, 222-241.
- Navrotsky, A., Forray, F.L., Drouet, C., 2005. Jarosite stability on Mars. *Icarus* 176, 250-253.
- Nordstrom, D.K., Archer, D.G., 2003. Arsenic thermodynamic data and environmental geochemistry: an evaluation of thermodynamic data for modeling the aqueous environmental geochemistry of arsenic, in: Welch, A.H., Stollenwerk, K.G. (Eds.), *Arsenic in ground water*. Kluwer Academic Publishers, Boston, pp. 1-25.
- Papike, J.J., Karner, J.M., Spilde, M.N., Shearer, C.K., 2006. Terrestrial analogs of martian sulfates: Major and minor element systematics of alunite-jarosite from Goldfield, Nevada. *Am. Mineral.* 91, 1197-1200.
- Powers, D.A., Rossman, G.R., Schugar, H.J., Gray, H.B., 1975. Magnetic behavior and infrared spectra of jarosite, basic iron sulfate, and their chromate analogs. *J. Solid State Chem.* 13, 1-13.
- Ripmeester, J.A., Ratcliffe, C.I., Dutrizac, J.E., Jambor, J.L., 1986. Hydronium ion in the alunite-jarosite group. *Can. Mineral.* 24, 435-447.
- Robie, R.A., Hemingway, B.S., 1995. Thermodynamic properties of minerals and related substances at 298.15 K and 1 Bar ( $10^5$  Pascals) pressure and at higher temperatures. U.S. Geological Survey, Washington, p. 461.
- Roca, A., Viñals, J., Arranz, M., Calero, J., 1999. Characterization and alkaline decomposition/cyanidation of beudantite-jarosite materials from Rio Tinto gossan ores. *Can. Metall. Q.* 38, 93-103.
- Romero, F.M., Prol-Ledesma, R.M., Canet, C., Alvares, L.N., Pérez-Vázquez, R., 2010. Acid drainage at the inactive Santa Lucia mine, western Cuba: Natural attenuation of arsenic, barium and lead, and geochemical behavior of rare earth elements. *Appl. Geochem.* 25, 716-727.
- Roussel, C., Néel, C., Bril, H., 2000. Minerals controlling arsenic and lead solubility in an abandoned gold mine tailings. *Sci. Total Environ.* 263, 209-219.
- Schwarzenbach, D., Abrahams, S.C., Flack, H.D., Gonschorek, W., Hahn, T., Huml, K., Marsh, R.E., Prince, E., Robertson, B.E., Rollett, J.S., Wilson, A.J.C., 1989. Statistical descriptors in crystallography: Report of the IUCr Subcommittee on Statistical Descriptors. *Acta Crystallographica Section A Foundations of Crystallography* 45, 63-75.
- Serna, C.J., Cortina, C.P., Garcia Ramos, J.V., 1986. Infrared and Raman study of alunite--jarosite compounds. *Spectrochimica Acta Part A: Molecular Spectroscopy* 42, 729-734.
- SGTE, 1999. Thermodynamic properties of inorganic materials compiled by SGTE, in: Martienssen, W. (Ed.), *Numerical data and functional relationships in science and technology*, Vol. IV/19A1. Springer-Verlag, Berlin, p. 406 p.
- Smith, A.M.L., Hudson-Edwards, K.A., Dubbin, W.E., Wright, K., 2006. Dissolution of jarosite  $[\text{KFe}_3(\text{SO}_4)_2(\text{OH})_6]$  at pH 2 and 8: Insights from batch experiments and computational modelling. *Geochim. Cosmochim. Acta* 70, 608-621.
- Toby, B.H., 2001. EXPGUI, a graphical user interface for GSAS. *J. Appl. Cryst.* 34, 210-213.
- Wagman, D.D., Evans, W.H., Parker, V.B., Halow, I., Bailey, S.M., Schumm, R.H., 1968. Selected values of chemical thermodynamic properties. Tables for the first thirty-four elements in the standard order of arrangement: NBS Technical Note 270-3.
- Wagman, D.D., Evans, W.H., Parker, V.B., Schumm, R.H., Halow, I., Bailey, S.M., Churney, K.L., Nuttall, R.L., 1982. The NBS tables of chemical thermodynamic properties. Selected values for inorganic and C1 and C2 organic substances in SI units. *J. Phys. Chem. Ref. Data* 11, 392.